

360° in Making Acellular and Biocompatible Xenografts for Surgical Applications

Aishwarya Satish, Jaikanth Chandrasekaran, Indhumathi T, Kotturathu Mammen Cherian and Balasundari Ramesh*

Frontier Lifeline Pvt Ltd, R80C, Ambattur Industrial Estate Road, Mugappair, Chennai, India

*Corresponding author: Balasundari Ramesh, Frontier Lifeline Pvt Ltd, R80C, Ambattur Industrial Estate Road, Mugappair, Chennai 600101, India, E-mail: balasundari2001@yahoo.com, drbalasundari@frontierlifeline.com

Received date: 03 Jun 2016; Accepted date: 15 Jul 2016; Published date: 20 Jul 2016.

Citation: Satish A, Chandrasekaran J, Indhumathi T, Cherian KM, Ramesh B (2016) 360° in Making Acellular and Biocompatible Xenografts for Surgical Applications. J Surg Open Access 2(6): doi <http://dx.doi.org/10.16966/2470-0991.132>

Copyright: © 2016 Satish A, et al. This is an open-access article distributed under the terms of the Creative Commons Attribution License, which permits unrestricted use, distribution, and reproduction in any medium, provided the original author and source are credited.

Abstract

There goes a famous saying - "We can judge the heart of a man by his treatment of animals". Now these animals help a man save his heart and vital organs through xenografts. The concept for xenograft is an explosive phenomenon in regenerative and tissue engineering. It has a wide application in many fields of medicine-Cardiology, Orthopedics, Dentistry, Gastrointestintology, Ophthalmology and Dermatology. This comprehensive review presents in detail the current methods and procedures followed in the preparation of a xenograft. It helps us in the optimal selection of a suitable method the potential barriers and challenges faced during processing and clinical application with a view towards the future direction.

Keywords: Xenograft; Decellularization; Cross-linking; Detoxification

Introduction

Grafting is the fundamental element on which the magnanimous fields of regenerative and transplantation medicines have been laid. Grafts differ from flaps on the absence of their own blood supply. The basis of grafting is directed differentiation. The four main categories of grafts based on their origin can be—Autograft (from same person), Isograft (between genetically identical twins), Allograft (between same species), Xenograft (between two different species).

Xenotransplantation refers to any procedure that involves the transplantation implantation, or infusion in to a human recipient of either 1) live cells, tissues, or organs from a nonhuman animal source or 2) human body fluids, cells, tissues, or organs that have had *ex-vivo* contact with live nonhuman animal cells tissues or organs The potential targets for xenograft harvesting are—Chimpanzee, baboon, pig and cattle. Xenografts are widely used for tissue engineering applications. Of these, porcine and bovine sources have vast applications (Figure 1). They are less expensive and readily available than homografts and allografts. The porcine dermis, pulmonary artery, aorta, submucosal membrane and bovine bone, pericardium, jugular vein are popular sources of tissue harvesting. Acellular xenografts have wide application in several fields like;

- **Cardiology:** Bioprosthetic heart valve constructed from bovine pericardial leaflets or porcine pulmonary valve are widely used in cardiac surgeries [1,2]. The valvular defects, aneurysm repair and the septal defects can be repaired with xenografts valves and pericardial patches.
- **Orthopedics:** Demineralized and deantigenized xenograft bone matrix can be used for orthopedic applications [3]. Likewise Krackow Achilles tendon repair can be augmented with use of xenograft like porcine dermal matrix [4].
- **Dentistry:** Xenograft is also used in dentistry for reconstruction of defects or replacement of missing teeth and can be used in combination with autogenous grafts [5].

- **Gastrointestintology:** Acellular xenograft has been used for hernia repair. The occurrence of infection, wound complication, gastrointestinal complication and recurrence of hernia is much lesser with xenograft mesh implants in comparison to synthetic mesh [6].
- **Ophthalmology:** It can also be used for complex scalp defects and eyelid defects [7]. The possibility of implanting decellularized porcine cornea as a xenograft in place of a defective cornea is being explored. Bovine pericardium has fewer complications when used as a wrap for hydroxyapatite implants to enable attachment of extraocular muscles in the artificial eye [8].
- **Dermatology:** Porcine skin has similar composition, pain reducing traits, hemostasis function and collagen content as the human skin [9]. It is used in cosmetology and burn wounds to ameliorate scar formation and infection. It can also be used to patch up an area after tumor removal, reducing chance of infection and fluid loss. In deep burns and scars, application of meshed acellular xenograft and the split-thickness skin autograft can induce tissue regeneration [9,10]. The application of xenograft provides a micro-environment that initiates migration and proliferation of epithelial cells. There are many commercially available xenografts in ready-to-use form like Apligraf® (skin construct comprised of neonatal foreskin keratinocytes and a matrix made from bovine collagen and fibroblasts), Integra® (bilaminar dermal substitute composed of an outer silicone layer and an inner layer made of cross-linked bovine collagen-glycosaminoglycan matrix) [11,12].
- Furthermore, use of Fetal Bovine Acellular Dermal Xenograft with tissue expansion has been currently implicated for Staged Breast Reconstruction (Pectoral extender), oncological hypopharyngeal defects reconstruction and interposition grafting in urological studies [13,14].

However pretreatment and intensive processing is necessary to remove antigenic factors, to reduce the rate of tissue rejection and inflammatory response triggered by the heterograft. The review deals with the processing of the xenograft starting from the collection of sample, decellularization, fixation and detoxification making it fit for clinical application.

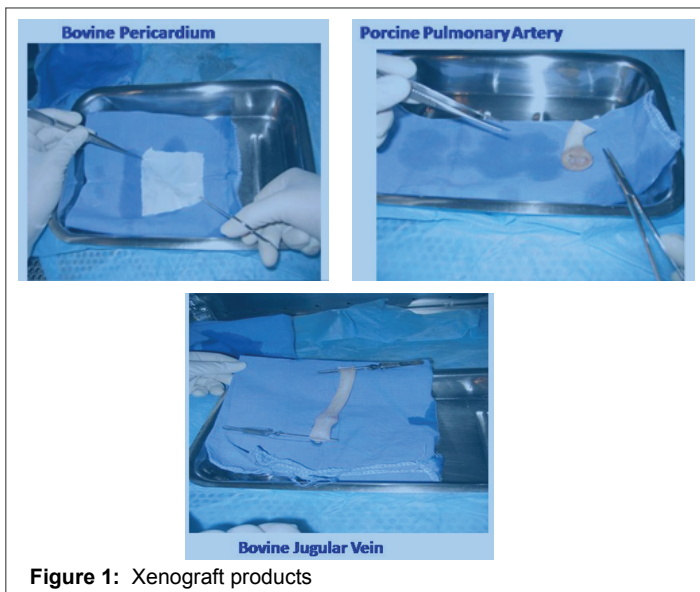


Figure 1: Xenograft products

Tissue harvesting and transportation

The animals selected for tissue harvesting are pre screened for zoonotic diseases and other risk factors. Desired tissue is collected under strict asepsis. The primary factor determining the success of this harvesting depends on the transport media. An ideal transport media should fulfill the following needs-maintain the viability and pH of cells, nourishment, inhibit microbial growth. However the choice of media mainly depends on the nature of tissue and the time of transportation. Some of the widely used media in various time-line are listed below for optimal selection.

Jee et al. [15] used Hanks' Balanced Salt Solution (HBSS) to store bovine pericardium at 4°C along with antibiotic cocktail of Cifran, Gentamycin, Streptomycin, Cephalosporin, Amphotericin B.

Balasundari et al. [16] used HBSS with cocktail of antibiotics like Cefuroxime, Gentamycin, Ciprofloxacin, Vancomycin, Amphotericin to transport the tissues at 4°C.

Phosphate buffered saline (PBS) with antibiotics like penicillin and streptomycin has been used to transport porcine aortic valve conduits [17].

Lee et al. [18] used 0.1M PBS pH 7.4 for the transportation of bovine pericardium.

0.9% Cold saline can be used to transport tissues from the slaughter house to the destination [19-22].

Roswell Park Memorial Institute medium [RPMI] can also be used as a transport media for the graft [23].

Golan et al. [24] used ice-cold RPMI to transport bovine fetal and human intestinal tissue.

Histocon is used as preservative-transport medium at 0-4°C. It is a cryoprotective and membrane-stabilizing agent [25].

Thomas et al. [26] had studied the efficacy of filtered coconut water as a transport medium, for avulsed tooth. It is sterile, containing a varied cocktail of sugars, amino acids, minerals, electrolytes. The preserving efficacy was compared with HBSS and milk. Results denote that coconut water is a better transport media compared to HBSS when storage is for more than 15 min and milk was inferior to HBSS [27].

The aim should be to deliver the tissue at the lab within 48 hours. The choice of media and additives added can be modified based on individual needs. However normal saline with antibiotics can be used if the transport time is less than two hours.

Decellularization

Decellularization is the initial step in preparing a xenograft. It involves removal of cells and debris present in the native tissue that might create an imbalance in calcium transport, increasing the intracellular calcium concentration. Which triggers Ca_2^+ ions binding to cell membrane phospholipids and form calcium phosphate crystals. Thus tissue decellularization reduces *in-vivo* calcification a critical phenomenon in surgical application [28]. Furthermore, it also removes the cellular antigenic components responsible for immunorejection specifically α -Gal and non- α -Gal T antigens [29].

Decellularization of graft tissues are generally performed using Sodium Dodecyl Sulphate, Triton X 100, Sodium Deoxycholate, Nuclease and Trypsin. However they are harsh to the tissues and even trace quantity remains in the tissue even after repeated wash. It has been reported that, these the trace quantity of detergents potentially impair the efficacy of the xenograft in surgical implantation [30]. Furthermore, Trypsin has been deduced by Yu et al. [17] and Zou et al. [31] to be harsh for the tissue. Repeated quantification of decellularizing agents is a critical step in processing Xenograft. Optimal selection of a suitable method is also vital in this process.

Successful decellularization should maintain elasticity of extracellular matrix [ECM] similar to original tissue and not cause structural or architectural changes in the graft tissue and should be reduced cytotoxic in nature. To achieve this various protocols have been adopted, they are listed briefly in table 1 [8,17,21,28,29,31-35], which aid in selection of suitable method for processing.

Cross-linking

Grafts are cross-linked to enhance mechanical stability. Interestingly, fixation also reduces immunogenicity of the tissue as it cross-links and masks the antigenic factors [36]. In relation to this here we details different cross linking agents current used in the processing and their advantages and disadvantages. Their relative benefits typically aid in selection better cross-linker

Glutaraldehyde: Glutaraldehyde is a dialdehyde that reacts with the amino group of lysine and hydroxylysine moieties to form cross links [37]. It is the most commonly used cross-linking agent that is stable and most effective to fix tissues. In addition, it also acts as a sterilizing agent against bacteria, virus and fungi. However, glutaraldehyde has several shortcomings as discussed in table 2 [15,18-21,29,32,34,38-47]. It is unable to stabilize all components of extracellular matrix of tissues, especially elastin and glycosaminoglycans [GAGs] [48]. Moreover, the residual unbound aldehyde groups can trap host plasma calcium contributing to tissue calcification [49]. The inflammatory response initiates activation of macrophages, which in turn triggers expression of matrix metalloprotein-9 [MMP-9] and tenascin-C [TN-C]. TN-C elevates alkaline phosphatase expression leading to calcification of heart valves [37,49]. In spite of these drawbacks, it is preferred due to long-term tissue stabilization and properties of preserving and sterilizing graft tissue.

Genipin: It is a naturally occurring cross-linker that is derived from geniposide, a compound isolated from fruit *Gardenia jasminoides*. It is less cytotoxic than glutaraldehyde. Genipin reacts spontaneously with amino acids or proteins to form dark blue pigments, thereby the aesthetic appearance is compromised [32].

1-ethyl-3-[3-dimethylaminopropyl] carbodiimide [EDC]: EDC catalyses the reaction of carboxylic acid with amine groups to form amide bonds via an O-acylisourea intermediate. The addition of N-hydroxysuccinimide [NHS] to EDC increases cross-linking efficiency [39]. Storage of the cross linked tissues in 25 mmol/L EDC reduced calcification in comparison to storage in glutaraldehyde [37].

| S.No | Chemical/ Method | Concentration | Xenograft tissues | Outcome | References |
|------|------------------------------------|---|---|---|------------|
| 1 | Sodium Dodecyl sulfate [SDS] | 0.1% SDS | Bovine pericardium | Complete decellularization, intact collagen ECM maintained | [28] |
| | | 0.10% in Tris buffer with nuclease for 48 h | Porcine aorta | Complete decellularization, ECM structure, hyperelastic mechanical integrity maintained. | [31] |
| | | 0.25% for 24 h at RT with osmotic shock | Bovine pericardium | Complete decellularization, intact collagen ECM, degree of cross-linking maintained, no protein denaturation | [33,35] |
| | | 0.5% in HEPES pH 7.4, for 24 h at 25°C | Bovine pericardium | Complete decellularization, T _d not affected, stress at break and thickness increased | [34] |
| | | 0.5% in PBS for 24 h at 37°C | Bovine pericardium | Collagen fibers became edematous, fragmented, and disorganized, nondetectable presence of carbohydrate antigen α-Gal, and T-antigen | [29] |
| 2 | Triton X [TX] | 1.0% in HEPES pH 7.4 for 24 h at 25°C | Bovine pericardium | Mean thickness reduced, increase in T _d Mechanical strength of graft maintained | [34] |
| | | 1.0% with 0.2% EDTA and nuclease in 10 mM Tris buffer at 37°C | Porcine aorta | Complete decellularization, ECM structure maintained, thickness reduced, hyperelastic mechanics integrity maintained | [31] |
| | | 0.9% in PBS for 48 h at 37°C | Bovine pericardium | Collagen fibers were fragmented, but organized. Nondetectable presence of carbohydrate antigen, α-Gal, and T-antigen | [29] |
| 3 | SDS+Triton X | 0.25% SDS pH 8 for 24 h followed by 0.5% Triton X-100 for 24 h | Bovine pericardium | Completely decellularized, significant reduction of DNA in the treated graft | [21] |
| 4 | Triton X+Sodium deoxycholate [DCA] | 0.5% triton X and 0.5% DCA in PBS | Bovine pericardium | Complete decellularization, ECM architecture and glucosaminoglycan content maintained, nondetectable presence of carbohydrate antigen, α-Gal, and T-antigen | [29] |
| | | 0.25% Triton X and 0.25% DCA at 37°C | Porcine aortic valve leaflets | Complete decellularization, no structural change or fractures | [17] |
| 5 | DCA+ Nucleases | 1% sodium deoxycholate for more than 40 h followed by nuclease treatment | Bovine pericardium and porcine pulmonary artery | Complete decellularization, no elastic fiber distortion, configuration of collagen type I and type IV maintained, fibronectin and laminin structure unaffected, GAG content retained. | [35] |
| 6 | Nuclease [DNase+RNase] | 40 μ/ml DNase and RNase for 30 min | Porcine cornea | complete decellularization | [8] |
| 7 | DCA+Trypsin | 0.05% trypsin for 12 h [with 0.02% EDTA] and 1% DCA for 24 h [with RNase and DNase] at 37°C | Porcine aortic valve leaflets | complete decellularization, structural changes observed [fibers loosely arranged], presence of small amount of cellular debris | [17] |
| 8 | Trypsin | 0.5% trypsin with 0.2% EDTA and nuclease in hypotonic Tris buffer for 48 h at 37°C | Porcine aorta | Complete decellularization, ECM structure distorted and fragmented, showing breakage of crosslink's and fibers | [31] |
| 9 | Freeze-thaw cycles | 3 cycles: -196°C liquid nitrogen for 30 min, thawing at 37°C for 30 min | Porcine cornea | complete decellularization, minimal damage to ECM | [8] |

Table 1: Detergents and chemicals involved in decellularization.

RT: Room Temperature; Td: Thermal denaturation temperature; EDTA: Ethylenediaminetetraacetic acid

Epoxide crosslinker: Alkyl polyepoxides have been used to crosslink tissues. However tissue penetration is low as the water solubility is less and require organic solvents. Polar polyepoxide compounds like triglycidyl amine are water soluble and should therefore penetrate tissues easily and be biocompatible [46].

Neomycin Sulphate: Cross linking of grafts with glutaraldehyde compromises the architecture of GAG and elastin, as it stabilizes only the collagen component. These components are lost during processing or storage of the tissue. To preserve the GAG content, Raghavan et al. [50] devised a protocol using Neomycin sulphate, a hyaluronidase inhibitor, preventing enzyme-mediated GAG degradation.

Dye mediated photooxidation: It does not require any harsh chemicals. In the presence of a suitable photosensitizer [Methylene blue, methylene green and rose Bengal dyes, certain amino acids can be oxidized by irradiation with visible light. Therefore, dye-mediated photooxidation treated grafts holds promise as a long term implantable biomaterial [47].

Several methods of cross-linking have been explored to overcome the drawback of glutaraldehyde. In certain studies glutaraldehyde was

replaced with silk fibroin and chitosan (1:1) cross-linkage with irradiation (electron beam). It reduces the risk of calcification and cytotoxicity. However it continues to be the most widely used agent to cross-link the tissues. It is highly recommended to develop a suitable method without using harsh chemicals. The details of cross-linking agents are detailed in table 2.

Detoxification

Formation of calcium-containing mineral deposits could result in cusp or vessel stiffness, loss of pliability, and blockage of the valve and could be attributed in part, to the toxic effect of cross-linkers [51]. In addition, the phosphorus group in phospholipids can bind to Calcium in extracellular fluid and initiate calcium phosphate crystal formation.

Neutralization of residual aldehyde groups: Pre-treatment of tissues with glutaraldehyde releases residual aldehyde groups due to polymerization. These residual aldehyde moieties enhance rate calcification of the xenograft and are cytotoxic [18,29]. Compounds like α-amino oleic acid is highly hydrophobic and caps the residual aldehyde groups in glutaraldehyde-cross linked tissues, reducing calcification

| S.No | Chemical/ Method | Concentration | Xenograft tissues | Outcome | Disadvantages | Reference |
|------|--|--|--|--|--|-----------|
| A | Glutaraldehyde [GA] | 0.2% in PBS in MES at RT | Porcine aortic root | Cross-linked graft | Broad calcium bands | [38] |
| | | 0.25% in 0.05M HEPES, pH 7.4 for 3 days at RT | Acellular Bovine Pericardium | Effective crosslinking, good mechanical strength, resistant to enzyme digestion | Colour change to dark yellow, Crosslink restrict impermeation of space fillers. Cytotoxicity high | [21] |
| | | 0.5% for 3 days at RT | Bovine Pericardium | Good cross-linking | High levels of inflammatory cells observed, increases risk of calcification | [32] |
| | | 0.5% in PBS pH 7.4 for 14 days at RT | Bovine Pericardium | Stable bonds formed indicated by decrease in lysine and histidine content | Residual free aldehyde groups of GA are cytotoxic and can result in tissue calcification | [18] |
| | | 0.5% in HEPES pH 7.4 for 2 days at RT | Acellular Bovine Pericardium | Stable crosslink of tissue | Cytotoxicity highest with GA-fixed tissue, high calcification noted and collagenous fiber degeneration observed | [39] |
| | | 0.6% in 50 mM HEPES pH 7.4 for 5 days | Acellular Bovine Pericardium | Crosslinked tissue | Generation of free aldehyde, resists enzymatic degradation | [29] |
| | | 0.6% in HEPES pH7.4 overnight at 22°C followed by 0.2% GA for 2 days | Bovine Pericardium | Stable crosslink of graft | Rigid and fragile graft, macrophage infiltration, expression of MMP-9 and TN-C | [19] |
| | | 0.6% in HEPES pH7.4 overnight at 22°C followed by 0.2% GA treatment for 2 days | Porcine aorta | Resistant to collagenase digestion indicating stable crosslink with aortic collagen | Elastase-mediated degradation is high, as GA does not stably bind to elastin | [40,41] |
| | | 0.6% in 50mM HEPES pH 7.4 for 24 h followed by 0.2% GA in HEPES for 6 days | Porcine aortic valve cusps and aortic wall | Stability of collagen | Significant loss of GAGs, hence increase in depth of buckling. | [42] |
| | | 0.625% in HBS for 24 h at 25°C | Acellular Bovine Pericardium | High crosslinking index, low residual amino group content | - | [34] |
| | | 0.625% in PBS pH 7.4 for 7 days at 4°C | Bovine Pericardium | Crosslinked tissue | Calcification observed in the graft tissue | [20] |
| | | 0.625% in PBS pH 7.4 for 10 days at 4°C | Bovine Pericardium | Cross-linking of tissue on reaction with amino acid residues of collagen | GA polymerizes and unreacted aldehyde groups present as remnants | [15] |
| | | 0.3125%, 0.625%, 1.2% increasing time of exposure 5, 10, 20, 30 min | Porcine pericardium | Crosslinked tissue | Higher calcification observed with increasing concentration; Increasing treatment time <i>decreases</i> calcification | [43] |
| | | 0.3125%, 0.625%, 1.2% increasing time of exposure 5, 10, 20, 30 min | Bovine Pericardium | Crosslinked tissue | Higher calcification observed with increasing concentration; Increasing treatment time <i>increases</i> calcification | [43] |
| | | 0.2% GA comparison with 0.6% GA | Bovine Pericardium | 0.2% concentration exhibited less calcification, inflammatory and antibody response than 0.6% in short duration exposure. | High concentration of GA has a toxic effect compared to lower concentration for short duration exposure | [44] |
| B | Genipin | 0.4% for 5 days at RT | Bovine Pericardium, Acellular Bovine Pericardium | Reduced calcification and lesser inflammatory cells compared to GA-crosslinked Pericardium | Formation of dark blue pigments on graft; Cross-linking potential is inferior to GA | [32] |
| | | 0.3% in 0.01 M PBS pH7.4 for 3 days at RT | Acellular Bovine Pericardium | Effective crosslinking of graft tissue with improved mechanical strength, Least cytotoxic | Dark blue colour on reaction. Less resistance to enzyme digestion compared to GA | [21] |
| C | 1-Ethyl-3-[3-dimethylaminopropyl] carbodiimide [EDC] | 0.1 M for 24 h at 25°C | Acellular Bovine Pericardium | Lower strain at break using TX as decellularizing agent | Cross-linking index lower than that with GA | [34] |
| | | 30 mM EDC and 6 mM NHS in 0.05 M MES pH 5.5 for 3 days at RT | Acellular Bovine Pericardium | Effective crosslinking and mechanical strength. When combined with space filler like Jeffamine, resistance to enzyme digestion improves. | Whitish colour on treatment. More cytotoxic than GA crosslinking. No much effect on calcification mitigation, susceptible to pronase digestion | [21] |

| | | | | | | |
|---|-------------------------------------|--|--|---|--|---------|
| | | 0.05 M EDC and 0.01 M NHS pH 5.5 for 2 days at RT | Acellular Bovine Pericardium | Calcific deposits and inflammatory cell infiltration reduced. Good preservation of collagen architecture. Cross-link efficiency found to be similar to GA cross-linking | - | [39] |
| | | 60 mmol/L Jeffamine in MES for 30 min at RT; then exposed to 0.3 mol/L EDC and 0.1 mol/L NHS agitating for 2.5 h at RT, pH 5 | GA-crosslinked Porcine aortic wall | Crosslinked tissue, Calcification level reduced and the subsequent storage in EDC reduced calcification further | Individually EDC could not reduce calcification | [38,45] |
| D | Polyepoxide [Triglycidyl amine:TGA] | 100 mM TGA in pH 7.4 borate mannitol buffer and its neutralization with 100 mM thiosulfate | Porcine aortic valve cusps and aortic wall | Porcine aortic valve cusp was Biocompatible, resistant to calcification | Porcine aortic wall did not show desired results. TGA preparation did not completely prevent long-term calcification | [46] |
| E | Neomycin trisulphate [NEO] | 1 mM NEO in MES [pH 5.5] for 1 h+ 30 mM EDC, 6 mM NHS in MES for 24 h+ 0.6% GA in HEPES [pH 7.4] for 24 h+0.2% GA in HEPES [pH 7.4] for 5 days | Porcine aortic valve cusps and aortic wall | Better stability against elastase and GAG degrading enzymes than GA treated tissues, better collagen stability. Depth of buckling was lower than GA-fixed graft | - | [42] |
| F | Dye mediated photooxidation | Grafts immersed in photoactive dye and exposed to broad-wavelength light source | Porcine aorta | Biostable, expressed low immunogenic response, non-inflammatory and resistant to calcification, can stabilize protein solution | Mild calcification in rat model, however in juvenile sheep model no significant calcification was observed | [47] |
| G | Ultraviolet irradiation | 15W UV lamp [254 nm] for 24 h at 4°C | Acellular Bovine Pericardium | Less inflammatory cell infiltration and calcification levels, better mechanical properties and cross-links comparable to GA, Retains pliability of tissue | Susceptible to pronase digestion, toxic to porcine fibroblast cells, collagen fiber degradation observed, less thermal stability | [39] |

Table 2: Chemicals and molecules used for cross linking of grafts

RT: Room temperature; EDTA: Ethylene diamine tetraacetic acid; GA: Glutaraldehyde; NHS: N-hydroxy succinimide; GAG: Glucosaminoglycan

by ~20% compared to glutaraldehyde treatment. AOA also acts as a detergent, extracting phospholipids reducing calcification sites in the cell membranes [37]. Commercial valves like Medtronic (Minneapolis, MN, USA) employ α -amino oleic acid as an anti-calcification agent for its valve (AOA[®]). Heparin detoxicates the aldehyde groups of glutaraldehyde [52]. No react[®] glutaraldehyde of Shelhigh Inc., is a heparin based detoxification method, wherein the glutaraldehyde-treated grafts are impregnated with surfactants [53]. However heparin demonstrated deleterious effects [54] and thus can be avoided. Sodium bisulfite, being a reductive agent, forms α -hydroxyl sodium sulfonate on reaction with aldehyde [55]. Citric acid, an organic acid with four hydroxyl groups, salifies amino groups and neutralizes free aldehyde group [56,57]. It also interacts with Schiff base entities generated on aldehyde-amino group reaction inducing hydrophilicity on surface of the collagen fiber. It was also deduced that citric acid detoxification improved endothelial progenitor cell adhesion and proliferation [29].

Various amino acids have been used to detoxify the residual aldehyde remaining after glutaraldehyde treatment. This could be due to the reaction between the amine groups of amino acid and the free aldehyde groups. The treatment conditions such as concentration, pH and reaction time influences the efficiency of anti-calcification [29]. Amino compounds when used alone as anti-calcificants displayed calcification in tissue, but when used in combination with organic solvents decreased calcification to low amounts [58].

GAGs and non-collagenous proteins seem to be involved mainly in the regulation of calcification processes. Hyaluronic acid (HA), a GAG, is a component of the ECM. It is biodegradable, non-toxic and is not immunogenic. The anti-calcification property of GAG was confirmed of

which HA reacts with the free aldehyde groups to form stable hydrazone bond. HA can also be used as a hydrogel on pericardium, by cross-linking the hydrazone bonds for a continuous anti-calcification effect [41,59]. In addition, space is created when the tissues are decellularized, which increases the possibility of calcium being deposited. This can be resolved by treating the tissues with space fillers before fixation [21]. The space fillers can be used synergistically with other anti-calcification techniques for a more positive effect.

Lyophilization is a freeze drying technique to store samples like tissues, preserving their architecture and viability. This process reduces the amount of residual aldehyde. Lyophilization is a favorable means of preservation of pericardium [60].

Phospholipid removal: The presence of phosphorus as phospholipids, in the cell membrane can lead to calcification. The calcium ions from plasma, reacts with phosphorus to form calcium phosphate deposits [28]. Hence the removal of phospholipids could reduce the incidence of calcification. Alcohol can reduce calcification by dissolving the cell membrane and disorder the acyl chains of phospholipids in the graft tissue [29]. Ethanol is used as anti-calcificant by St. Jude Medical, Minneapolis, MN, USA (Epic[®] valves), and along with Tween-80, it is used by Edwards Life sciences Corporation, Santa Ana, CA, USA for its product XenoLogiX[®] Long chain alcohol (LCA) has structure resembling the phospholipids. LCA would replace the phospholipids and decreases chance of calcification [60]. Short chain alcohol (SCA) used in combination with LCA would improve solubility in aqueous solutions, reduce micelle formation, and improve penetration into thick tissues [36].

| S.No | Chemical/ Method | Concentration | Xenograft tissues | Outcome in animal experiments | Reference |
|--|------------------------------|--|---|---|-----------|
| a] Neutralization of residual aldehyde groups | | | | | |
| 1 | Alpha amino oleic acid [AOA] | Porcine aortic wall tissue from Medtronic Freestyle Valve incorporating AOA | GA cross-linked Porcine aorta | Surface calcium bands less condensed, scattered calcification sites. AOA is more efficient in reducing calcification when followed by EDC crosslink | [38] |
| | | Porcine aortic wall tissue from Medtronic Freestyle Valve incorporating AOA | Jeffamine/EDC cross-linked Porcine aorta | Dramatic decrease in calcification. | [38] |
| 2 | Heparin | Initial exposure to Chitosan, 0.1% heparin pH 7.4, for 7 days at 4°C followed by 0.1M sodium borohydrate [NaBH ₄], pH 8.8 at RT for 24 h | GA crosslinked bovine pericardium | Significant reduction in calcification, but change in mechanical function was noticed | [52] |
| | | Shelhigh aortic stentless conduit | GA crosslinked bovine pericardium with incorporated porcine valve | Disintegration of graft and rupture of the aortic root. | [54] |
| 3 | Sodium bisulfate | 40% at 4°C for 24 h | GA and Genipin cross-linked Bovine Pericardium | Degree of cross-linking and tissue strength maintained, prevents calcification, | [32] |
| 4 | Citric acid | 10% citric acid in PBS for 30 min | Acellular GA fixed Bovine Pericardium | Free aldehyde detoxified to 79.50 ± 3.63% on reaction with cysteine, higher tensile strength | [29] |
| | | 5% & 10% for 30 min | GA crosslinked Bovine Pericardium | 10% citric acid showed better reduction in free aldehyde concentration | [56] |
| | | 3.8%, pH 7.4 for 48 h at 37°C | GA crosslinked Bovine Pericardium | Calcium levels minimized compared to control | [64] |
| | Amino acids | | | | |
| 5 | Arginine [Arg] | 2% in PBS pH 11 at varying exposure time as 2 h, 6 h and 2 days | GA cross-linked Bovine Pericardium | Arg acts as filling agent and makes graft impermeable to plasma calcium, reducing calcification. Increased resistance to collagenase digestion. High durability, low protein adsorption and platelet adhesion, enhanced blood compatibility | [15] |
| | | 0.1 M L-Arg, pH 11 for 48 h at 37°C followed by 0.1 M NaBH ₄ for 48 h at RT | GA cross-linked Bovine Pericardium | Increases tensile strength and thickness of graft. The thermal stability is maintained. No effect on calcification was observed. | [65] |
| 6 | Glycine | 0.2 M in PBS, pH 7.4 at 4°C for 24 h | Acellular GA fixed Bovine Pericardium | Micro-structure of graft not altered, degree of cross-linking and tissue strength unaffected | [32] |
| | | 0.1 M in acetic acid buffered solution [pH 4.5] for 48 h at 37°C; then in PBS buffered 0.1M Sodium Borohydrate solution pH 7.4 for 24 h | GA cross-linked Bovine Pericardium | Structure, degree of crosslinking and tissue strength not affected, nearly complete inhibition of calcification | [19] |
| 7 | L-Glutamic acid | 0.2% in 0.1 M PBS for 24 h 20°C | GA cross-linked Bovine Pericardium | Pronounced inflammatory response and calcification. | [28] |
| | | 0.2% in 0.1 M PBS for 24 h 20°C | Acellular GA cross-linked Bovine Pericardium | Reduces inflammatory reaction and calcification | [28] |
| | | 0.025 mol/L in borate buffer adjusted to alkaline pH | GA cross-linked Bovine Pericardium | Natural structure of collagen and elastin becomes fragmented with increasing processing time | [66] |
| 8 | L-Lysine (Lys) | 25, 50 & 100 mM at 37°C, 2 days | 0.2% & 0.7% GA cross-linked Porcine aorta | Decreased calcification. | [37] |
| | | 0.1 M for 48 h at 37°C | GA cross-linked, lysine treated Bovine Pericardium | Significant reduction in calcification | [67] |
| | | 0.1 M Lys, pH 7.6 for 48 h at 37°C followed by 0.1 M NaBH ₄ for 48 h at RT | GA cross-linked Bovine Pericardium | Calcium deposits observed in the fibrous layer of pericardium. Tensile strength of treated graft is improved | [65] |
| 9 | Urazole | 0.1 M in PBS for 1 week at RT | GA cross-linked Bovine Pericardium | Calcification observed, but on combination with alcohol significant reduction in calcium levels | [58] |
| 10 | Hyaluronic acid (HA) | HA-adipic dihydrazide (ADH) synthesis using EDC, pH 4.8 for 2 h. | GA cross-linked Bovine Pericardium | Decrease in calcification by 84.5% as HA sequesters calcium ions preventing hydroxyapatite nucleation | [59] |

| 11 Space Fillers | | | | | |
|-------------------------|--|--|---|--|---------|
| a | Jeffamine (polypropylene glycol-bis-aminopropyl ether) | 0.06 M in 0.25 M MES pH 5 for 24 h at RT | Acellular Bovine Pericardium | Tissues become thicker. Jeffamine increases cytotoxicity. | [21] |
| b | Polyethylene glycol | 50% in 0.01 M PBS pH 7.4 for 24 h at RT | Acellular Bovine Pericardium | Tissues become thicker. Good anti-calcification effect. | [21] |
| c | Polyacrylamide | 30 g acrylamide/ bisacrylamide in 37:1 ratio and 4% DMPA in 0.01 M PBS pH 7.4 for 24 h at RT | Acellular crosslinked Bovine Pericardium | Tissues become thicker. Strength increases on space filling with polyacrylamide | [21] |
| 12 | Sodium borohydrate [NaBH ₄] | 0.1 M Sodium borohydrate | GA crosslinked bovine pericardium | Calcification levels are reduced. Neutralizes surface free aldehyde group created on Glut fixation to hydroxyl groups. | [52] |
| | | 0.08 M NaBH ₄ for 24 h at RT in Glycine buffer and carbonate buffer individually (pH 7.5) | Porcine aortic valve cusps | Not much effective in reducing calcification. Has limited half life and is pH sensitive. Combined with alcohol treatment improved anti-calcification property and was most effective in carbonate buffer | [68] |
| | | 0.08 M NaBH ₄ for 24 h in carbonate buffer (pH 10.3) | GA fixed Porcine aortic valve cusp | Significant calcium deposits observed | [22] |
| 13 | Sodium cyanoborohydride | 0.08 M Sodium cyanoborohydride for 24 h at RT in 0.2 M HEPES, 0.1 M NaOH, 0.15 M glycine (pH7.5) | Porcine aortic valve cusps | Rare and irregular pattern of calcification observed in combination with alcohol. | [68] |
| 14 | Titanium coating | Plasma deposition of titanium | GA fixed Bovine Pericardium | Titanium exposure decreased free aldehyde concentration generated by GA treatment | [56] |
| 15 | Aldehyde dehydrogenase | 1 ml solution for 24 h | GA fixed Bovine Pericardium | Displayed good reduction in free aldehyde concentration | [56] |
| 16 | Sequential treatment [Citric acid, Aldehyde dehydrogenase, Titanium coating] | Same reaction conditions as mentioned individually | GA crosslinked Bovine Pericardium | A combination of the three methods mitigated free aldehyde concentration. 94.1% endothelial cell survival in these grafts | [56] |
| 17 | Lyophilization | | Acellular EDC crosslinked Bovine Pericardium | reduces free aldehyde content | [30] |
| | | | Bovine pericardium | Stiffness of valve leaflets increased. Opening and closing of valve altered, increase in gradient of conduit compared to untreated graft | [69] |
| | | | GA fixed bovine pericardium | Decreased inflammatory response after six months of implantation, did not increase chance of thrombus formation | [70] |
| | | | GA fixed bovine pericardium | Decreases cytotoxicity, mechanical property maintained. | [60] |
| b] Phospholipid removal | | | | | |
| 18 | Organic solvent | 80% ethanol for 24 h at pH 7.4 | GA cross-linked Porcine aortic valve cusp | Calcification levels reduced with occasional occurrence in central region of graft. Optimal results when combined with a reducing agent like sodium borohydrate | [68] |
| | | 80% ethanol in HEPES (pH 7.4) for 24 h | GA cross-linked Porcine aortic valve cusp | Reduction in calcium levels, propensity to buckling is higher | [22] |
| | | 80% ethanol for 24 h+0.1 M NaBH ₄ for 48 h | GA cross-linked Bovine Pericardium | Anti-calcification properties observed. | [65] |
| | | 75% ethanol+5% octanol 2 days at RT | GA & Genipin fixed Bovine Pericardium | Reduction in calcium depots | [32] |
| | | 77.5% ethanol+2.5% octanol/octanediol for 48 h | GA cross-linked/ urazole treated Bovine Pericardium | Calcification significantly reduced and tissue architecture displayed no deterioration. Combination with amino compound like urazole/glutamic acid gave better results | [58] |
| | | 75% ethanol+5% octanediol, 2 days at RT | GA and Genipin cross-linked Bovine Pericardium | Excellent anti-calcification | [32] |
| | | 40% ethanol+5% octanediol in HEPES for 68 h | Bovine pericardium and porcine valve | Reduces calcification potential and phospholipid content, and biocompatibility. Elastin and collagen fiber content maintained | [71,72] |
| | | 70% ethanol+10% isopropanol, 2 days at RT | GA and Genipin cross-linked Bovine Pericardium | Excellent anti-calcification | [32] |

| | | | | | |
|--------------------------------------|---|---|--|--|------|
| 19 | Organic solvent+Glycine [Synergistic approach] | 65% ethanol+5% octanol; 0.1 M glycine at pH 4.5 | GA cross-linked Bovine Pericardium | No structural changes, Low level of calcification noticed after a short duration of implantation; could be beneficial in long-term | [18] |
| 20 | Alcohol [ethanol+octanol]+Glycine | 75% ethanol, 5% octanol 2 days at RT; 0.1 M glycine pH 7.4 for 24 h RT | Acellular Bovine Pericardium | Mitigates calcification and cytotoxicity by extracting phospholipids using alcohol and detoxifying the free aldehyde remnants using glycine | [39] |
| 21 | Tannic acid | 0.3% in GA in Na ₂ HPO ₄ buffered saline pH5.5 for 4 days at 22°C | GA cross-linked Bovine Pericardium | Reduction in calcification [trivial levels of calcium detected], reduced MMP-9 and TN-C expression and macrophage infiltration | [19] |
| | | 0.3% in GA in Na ₂ HPO ₄ buffered saline pH5.5 for 4 days at 22°C | GA cross-linked porcine aorta | Stabilizes elastin, preventing elastase-mediated degradation and elastin-oriented calcification | [40] |
| c] Crystallization inhibitors | | | | | |
| 22 | Phytate | 0.25, 0.5, and 1.0 mg/l; incubated with graft for 96 h at 37°C | GA cross-linked Bovine Pericardium | Potent calcification inhibitory effect. Drastic decrease in calcification levels even at 0.25 mg/l. It is less toxic and inhibits hydroxyapatite crystallization | [20] |
| 23 | Pyrophosphate | 1 mg/l & 0.5 mg/l; incubated with graft for 96 h at 37°C | GA cross-linked Bovine Pericardium | 1 mg/l concentration showed less calcification and 0.5 mg/l displayed similar calcification compared to control of GA treated sample | [20] |
| 24 | Etidronate | 1 mg/l & 0.5 mg/l; incubated with graft for 96 h at 37°C | GA cross-linked Bovine Pericardium | 1 mg/l concentration showed less calcification and 0.5 mg/l had no effect on calcification inhibition | [20] |
| 25 | 2-mercaptoethylidene-1,1-bisphosphonic acid (MABP) | 20 mM MABP in borate mannitol buffer [pH 7.4] overnight incubation | Polyepoxide crosslinked Porcine aortic valve cusps and aortic wall | Complete inhibition of calcification | [46] |
| 26 | EDTA | 11% EDTA for a period of 48 h | GA cross-linked Bovine Pericardium | Calcium levels lower than control group | [64] |
| | | 100 µg/ml in PBS at 4°C for 24 h followed by GA fixation, then second exposure to 100 µg/ml in PBS at RT for 24 h | GA cross-linked Bovine Pericardium | Diminished calcium crystal formation and decreases aldehyde-initiated calcification. Reduces calcification but does not prevent it | [73] |
| d] Other methods | | | | | |
| 27 | Chitosan | 0.125% chitosan pH 6 at 4°C for 72 h | GA fixed bovine pericardium | Calcification levels were not mitigated and deformation in mechanical behavior was observed | [52] |
| 28 | Diethyl ether | 70% ether [pH 3] continuous stirring at RT for 4 h | GA fixed bovine pericardium | Good anti-calcification effect, levels of calcium ions dropped to 3.69 µg/mg from 194.5 µg/mg of control | [34] |
| 29 | Thermal treatment | 50°C for 2 days | GA fixed bovine pericardium | Inhibits calcification, no mechanical deformation | [34] |
| 30 | Sequential treatment (chitosan, heparin and others) | Same reaction conditions as mentioned individually | GA crosslinked bovine pericardium | Efficient, showing drastic reduction in calcium ion levels. Mechanical behaviour changed on treatment, but considered adequate | [34] |
| 31 | Cysteine (Cys) | 0.25-2.0 w/v cysteine for 24 h at 25°C | Acellular GA crosslinked Bovine Pericardium | Cys utilizes residual aldehyde and decreases calcification. Cys might also exchange nitric oxide with S-nitrosothiols [donors] <i>in vivo</i> and this might reduce platelet adhesion. | [34] |
| | | 0.25-2.0 w/v cysteine for 24 h at 25°C | Acellular EDC fixed Bovine Pericardium | Incorporation of cysteine was lower | [34] |
| 32 | Nitric Oxide | NO donor DETA-NONOate 5-1s00 µM, sodium nitroprusside [SNP] 3 µM | Porcine Aortic Valve Cells | Inhibit TGF-β1 mediated calcification by increase in cGMP concentration. | [62] |

Table 3: Detoxification of cross linked grafts

RT: Room temperature; GA: Glutaraldehyde; EDC: 1-Ethyl-3-[3-dimethylaminopropyl] carbodiimide

Tannic acid [TA] is a hydrolysable polyphenol. Glutaraldehyde fixation leads to elastin degradation, decreasing the mechanical stability. TA forms multiple bonds with elastin and collagen. Preservation of elastin content inhibits elastin-oriented calcification of glutaraldehyde-treated tissue [46].

Crystallization inhibitors: Crystallization inhibitors prevent development of calcium crystals by binding to the crystal nucleus. Pyrophosphate, a naturally occurring polyphosphate present in serum and

urine was used to prevent calcification by binding to hydroxyapatite from the 1960's [61]. However pyrophosphate inhibits calcification only when injected, as it hydrolyzes on oral administration and is inactivated. Hence bisphosphonate, a stable analogue of pyrophosphate and a calcium-binding compound was synthesized [61]. It is known as crystal poison as it binds to hydroxyapatite crystals and inhibits further crystal growth [59]. Ethylenediaminetetraacetic acid (EDTA)

is a chelating agent which can be used to minimize calcification by sequestering metal ions like Ca^{2+} and reducing the dimensions of the crystal. EDTA also inhibits matrix metalloproteinase. Nevertheless it was deduced that none of these methods prevent the process of crystal formation, but only minimizes it.

Nitric oxide and other methods: Nitric oxide donors inhibit TGF- β 1 mediated calcification by increase in intracellular cGMP and decreased superoxide concentration. TGF- β 1 is a cytokine which plays a role in aortic valve stenosis and could induce the formation of cell aggregates leading to calcific nodules in aortic valve cell cultures *in vitro* [62]. Nitric oxide reduces the thrombogenicity of target tissue by cGMP dependent and independent methods, acting in the form of S-nitrosothiols [like cysteine] [63]. Ether and chitosan also enable detoxification of graft tissue. The details are tabulated in table 3 [15,18-22,28-30,32,34,37-40,46,52,54,56,58-60,64-73].

Novel approach: incorporating endothelial cells and/or nanotechnology

The novel approaches that may help improve this field to serve the human race can be

- Incorporation of nanoparticles to increase the efficacy and aid in the healing of chronic wounds and ulcers.
- Addition of anti coagulants in valve xenografts with sustained/controlled release.
- Addition of anti cancer drugs in sites of tumour removal seeding of endothelial cells and collagen in the decellularised tissue can improve the durability and bio compatibility of xenografts. These tissues are found to be non-cytotoxic, non-immunogenic, non-calcific and had an improved resistance to thrombogenicity [74]. This approach would decrease the complications arising from compatibility issues and can be applied to generate allogenic/autogenic grafts by culturing the endothelial cells on biodegradable polymers [75].
- Coating xenografts with immune suppressive agents may help to prevent rejection. Clinical research into these methods is necessary for clinical and medical application.

Barriers in xenotransplantation

a) Immunological barriers: Humans have Xenoregulated Natural Antibodies that lead to hyperacute rejections when they receive xenograft from discordant species. This rejection is mounted on the basis that humans lack α -1,3 galactosyl transferase enzyme. The target for most human non-Gal xenoantibodies is the sialic acid N-glycolylneuraminic acid (Neu5Gc) synthesised by the CMAH (cytidine monophospho-N-acetylneuraminic acid hydroxylase) gene, which is inactive in humans [76]. It can be overcome by use of genetically engineered knockout transgenic animals. The risk of transplant rejection can be estimated by measuring the panel reactive antibody levels. Cases of dysregulated coagulation episodes have also been reported. Insertional mutagenesis is a serious entity that needs to be explored in depth.

b) Biological barriers: Humans are posed to the risk of xenozoonosis following transplant. The porcine endogenous retroviruses (PERV), Swine influenza virus, Japanese Encephalitis virus, Hepatitis E virus, Nipah virus, Bubaline herpes virus, Capripoxvirus and bovine arbovirus pose a serious threat of viral xenozoonosis. Furthermore, transmissions of prion diseases such as Cruetzfeld Jacobsons disease, bacterial and nematode infections have also been a potential barrier [77]. Harvesting organs from Specific pathogen free animals may control the issues of xenozoonosis.

Conclusion

This detailed review illustrates the step wise methods in making a xenograft, the challenges met with and possible methods to overcome them. The mechanical strength of the processed xenograft is equivalent to or higher than the homograft. The anti-calcification treatment of the graft reduces the calcifying potential of the xenograft to levels comparable to homograft. Various detoxification protocols neutralize the toxic residues that remain after the chemical treatment, thus making it safe for human use. The barriers need to be taken into mind and dealt with accordingly. The prospects of making a xenograft more compatible and less toxic can be explored further, to make it an ideal one. Slaughtering of animals for graft purpose can be minimized by the use of other alternates such as homografts, prosthetic and biodegradable synthetic grafts.

Acknowledgement

We thank our colleagues for helpful discussions and reviewing the manuscript.

Funding Sources

This work was funded by Frontier Lifeline Hospital & Dr. K. M. Cherian's Heart Foundation.

References

1. Shibuya N, Jupiter DC (2015) Bone Graft Substitute: Allograft and Xenograft. *Clin Podiatr Med Surg* 32: 21-34.
2. Bre LP, McCarthy R, Wang W (2014) Prevention of bioprosthetic heart valve calcification: strategies and outcomes. *Curr Med Chem* 21: 2553-2564.
3. Bauer TW, Muschler GF (2000) Bone graft materials. An overview of the basic science. *Clin Orthop Relat Res* 371: 10-27.
4. Wisbeck JM, Parks BG, Schon LC (2012) Xenograft scaffold full-wrap reinforcement of Krackow achilles tendon repair. *Orthopedics* 35: e331-e334.
5. Mahesh L, Lahori M, Narayan TV, Shukla S (2010) Management of Failed Implant Site with Symphyseal Graft in Combination with Xenograft and 4-year Follow-up Post-reimplantation. *Int J Oral Implantol Clin Res* 1: 163-167.
6. DeNoto G III, Reaven N, Funk S (2013) Ventral hernia retrospective cost analysis of primary repair, repair with synthetic mesh, and repair with acellular xenograft implant. *Open Access Surgery* 6: 23-32.
7. Yoeuek E, Bayyoud T, Maurus C, Hofmann J, Spitzer MS, et al. (2012) Reconstruction of corneal stroma with decellularized porcine xenografts in a rabbit model. *Acta Ophthalmol* 90: e206-e210.
8. Lee W, Miyagawa Y, Long C, Cooper DK, Hara H (2014) A comparison of three methods of decellularization of pig corneas to reduce immunogenicity. *Int J Ophthalmol* 7: 587-593.
9. Chen X, Feng X, Xie J, Ruan S, Lin Y, et al. (2013) Application of acellular dermal xenografts in full-thickness skin burns. *Exp Ther Med* 1: 194-198.
10. Pan S, Zhu X, Pan Y, Su W, Huang Q, et al. (2002) Application of meshed acellular dermis xenograft (pigskin) with scalp thin skin autograft in 15 patients. *Zhonghua Zheng Xing Wai Ke Za Zhi* 18: 273-275.
11. Gupta M, Singh AD, Rundle PA, Rennie IG (2004) Bovine pericardium (Ocuguard) wrap for hydroxyapatite implants. *Br J Ophthalmol* 88: 834-835.
12. Raimer DW, Group AR, Pettitt MS, Nosrati N, Yamazaki ML, et al (2011) Porcine xenograft biosynthetic wound dressings for the management of postoperative Mohs wounds. *Dermatol Online J* 17: 1.

13. Endress R, Choi MSS, Lee GK (2012) Use of fetal bovine acellular dermal xenograft with tissue expansion for staged breast reconstruction. *Ann Plast Surg* 68: 338-341.
14. Mehrdad MM, Meininger MS, Lacey MS (2012) Veritas® bovine pericardium for immediate breast reconstruction: a xenograft alternative to acellular dermal matrix products. *Mofid Eur J Plast Surg* 35: 717-722.
15. Jee KS, Kim YS, Park KD, Kim Y (2003) A novel chemical modification of bioprosthetic tissues using L-arginine. *Biomaterials* 24: 3409-3416.
16. Balasundari R, Gupta R, Sivasubramanian V, Chandrasekaran R, Arumugam S, et al. (2007) Complete microbe free processed porcine xenograft for clinical use. *Indian J Thorac Cardiovasc Surg* 23: 240-245.
17. Yu BT, Li WT, Song BQ, Wu YL (2013) Comparative study of the Triton X-100-sodium deoxycholate method and detergent-enzymatic digestion method for decellularization of porcine aortic valves. *Eur Rev Med Pharmacol Sci* 17: 2179-2184.
18. Lee C, Kim SH, Choi SH, Kim Y (2011) High-concentration glutaraldehyde fixation of bovine pericardium in organic solvent and post-fixation glycine treatment: *in vitro* material assessment and *in vivo* anticalcification effect. *Eur J Cardiothorac Surg* 39: 381-387.
19. Wang D, Jiang H, Li J, Zhou JY, Hu SS (2008) Mitigated calcification of glutaraldehyde-fixed bovine pericardium by tannic acid in rats. *Chin Med J* 121: 1675-1679.
20. Grases F, Sanchis P, Costa-Bauzá A, Bonnin O, Isern B, et al. (2008) Phytate inhibits bovine pericardium calcification *in vitro*. *Cardiovasc Pathol* 17: 139-145.
21. Jeong S, Yoon EJ, Lim HG, Sung SC, Kim YJ (2013) The effect of space fillers in the cross-linking processes of bioprosthesis. *Biores Open Access* 2: 98-106.
22. Raghavan D, Shah SR, Vyavahare NR (2010) Neomycin fixation followed by ethanol pretreatment leads to reduced buckling and inhibition of calcification in bioprosthetic valves. *J Biomed Mater Res B Appl Biomater* 92: 168-177.
23. Tedder ME, Liao J, Weed B, Stabler C, Zhang H, et al. (2009) Stabilized collagen scaffolds for heart valve tissue engineering. *Tissue Eng Part A* 15: 1257-1268.
24. Golan L, Gonen E, Yagel S, Rosenshine I, Shpigel NY (2011) Enterohemorrhagic *Escherichia coli* induce attaching and effacing lesions and hemorrhagic colitis in human and bovine intestinal xenograft models. *Dis Model Mech* 4: 86-94.
25. Korsgren O, Wallgren AC, Satake M, Karlsson-Parra A (1999) Xenograft rejection of fetal porcine islet-like cell clusters in the rat: effects of active and passive immunization. *Xenotransplantation* 6: 271-280.
26. Thomas T, Gopikrishna V, Kandaswamy D (2008) Comparative evaluation of maintenance of cell viability of an experimental transport media "coconut water" with Hank's balanced salt solution and milk, for transportation of an avulsed tooth: An *in vitro* cell culture study. *J Conserv Dent* 11: 22-29.
27. Sanghavi T, Shah N, Parekh V, Singbal K (2013) Evaluation and comparison of efficacy of three different storage media, coconut water, propolis, and oral rehydration solution, in maintaining the viability of periodontal ligament cells. *J Conserv Dent* 16: 71-74.
28. Collatusso C, Roderjan JG, Vieira ED, da Costa FDA, Noronha Ld, et al. (2012). decellularization Effect of SDS in preventing calcification of bovine pericardium fixed in glutaraldehyde. *Studo in rats. Rev Bras Cir Cardiovasc* 27: 88-96.
29. Mathapati S, Bishi DK, Guhathakurta S, Cherian KM, Venugopal JR, et al. (2013) Biomimetic acellular detoxified glutaraldehyde cross-linked bovine pericardium for tissue engineering. *Mater Sci Eng C Mater Biol Appl* 33: 1561-1572.
30. Mathapati S, Galla S, Sankaranarayanan K, Verma RS, Cherian KM, et al. (2010) Qualitative and quantitative detection of sodium deoxycholic acid in decellularized tissue. *Indian J Thorac Cardiovasc Surg* 26: 129-131.
31. Zou Y, Zhang Y (2012) Mechanical evaluation of decellularized porcine thoracic aorta. *J Surg Res* 175: 359-368.
32. Lim HG, Kim SH, Choi SY, Kim YJ (2012) Anticalcification effects of decellularization, solvent, and detoxification treatment for genipin and glutaraldehyde fixation of bovine pericardium. *Eur J Cardiothorac Surg* 41:383-90.
33. Hwang SW, Kim YJ, Kim SH, Choi SH (2010) Anti-calcification Effects in Decellularized and Variously Fixed Bovine Pericardium. *Korean J Thorac Cardiovasc Surg* 43:235-245.
34. Mendoza-Novelo B, Cauich-Rodríguez JV (2009) The effect of surfactants, crosslinking agents and L-cysteine on the stabilization and mechanical properties of bovine pericardium. *J Appl Biomater Biomech* 7: 123-131.
35. Galla S, Mathapathi S, Nayak VM, Cherian KM, Guhathakurtha S (2010) Analytical study to evaluate the extracellular matrix in processed acellular xenografts. *Indian J Thorac Cardiovasc Surg* 26: 132-138.
36. Manji RA, Zhu LF, Nijjar NK, Rayner DC, Korbitt GS, et al (2006) Glutaraldehyde-fixed bioprosthetic heart valve conduits calcify and fail from xenograft rejection. *Circulation* 114: 318-327.
37. Zilla P, Brink J, Human P, Bezuidenhout D (2008) Prosthetic heart valves: catering for the few. *Biomaterials* 29: 385-406.
38. Zilla P, Bezuidenhout D, Human P (2005) Carbodiimide treatment dramatically potentiates the anticalcific effect of alpha-amino oleic acid on glutaraldehyde-fixed aortic wall tissue. *Ann Thorac Surg* 79: 905-910.
39. Park S, Kim SH, Lim HG, Lim C, Kim YJ (2013) The Anti-calcification Effect of Dithiobispropionimidate, Carbodiimide and Ultraviolet Irradiation Cross-linking Compared to Glutaraldehyde in Rabbit Implantation Models. *Korean J Thorac Cardiovasc Surg* 46: 1-13.
40. Isenburg JC, Simionescu DT, Vyavahare NR (2005) Tannic acid treatment enhances biostability and reduces calcification of glutaraldehyde fixed aortic wall. *Biomaterials* 26: 1237-1245.
41. Lovekamp JJ, Simionescu DT, Mercuri JJ, Zubiata B, Sacks MS, et al. (2006) Stability and function of glycosaminoglycans in porcine bioprosthetic heart valves. *Biomaterials* 27: 1507-1518.
42. Raghavan D, Starcher BC, Vyavahare NR (2009) Neomycin binding preserves extracellular matrix in bioprosthetic heart valves during *in vitro* cyclic fatigue and storage. *Acta Biomater* 5: 983-992.
43. Sinha P, Zurakowski D, Kumar TK, He D, Rossi C, et al. (2012) Effects of glutaraldehyde concentration, pretreatment time, and type of tissue (porcine versus bovine) on postimplantation calcification. *J Thorac Cardiovasc Surg* 143: 224-227.
44. Umashankar PR, Arun T, Kumari TV (2011) Short duration gluteraldehyde cross linking of decellularized bovine pericardium improves biological response. *J Biomed Mater Res A* 97: 311-320.
45. Zilla P, Bezuidenhout D, Torrianni M, Hendriks M, Human P (2005) Diamine-extended glutaraldehyde- and carbodiimide crosslinks act synergistically in mitigating bioprosthetic aortic wall calcification. *J Heart Valve Dis* 14: 538-545.
46. Rapoport HS, Connolly JM, Fulmer J, Dai N, Murti BH, et al. (2007) Mechanisms of the *in vivo* inhibition of calcification of bioprosthetic porcine aortic valve cusps and aortic wall with triglycidylamine/mercapto bisphosphonate. *Biomaterials* 28: 690-699.
47. Moore MA, Adams AK (2001) Calcification resistance, biostability, and low immunogenic potential of porcine heart valves modified by dye-mediated photooxidation. *J Biomed Mater Res* 56: 24-30.

48. Páez JMG, Jorge-Herrero E (1999) Assessment of Pericardium in Cardiac Bioprosthesis. A Review. *J Biomater Appl* 13: 351-388.
49. Miller JD, Weiss RM, Heistad DD (2011) Calcific Aortic Valve Stenosis: Methods, Models, and Mechanisms. *Circ Res* 108: 1392-1412.
50. Raghavan D, Simionescu DT, Vyavahare NR (2007) Neomycin prevents enzyme-mediated glycosaminoglycan degradation in bioprosthetic heart valves. *Biomaterials* 28: 2861-2868.
51. Schmidt CE, Baier JM (2000) Acellular vascular tissues: natural biomaterials for tissue repair and tissue engineering. *Biomaterials* 21: 2215-2231.
52. Baucia JA, Net LRM, Rogero JR, Nascimento N (2006) Anti-calcifying treatment of glutaraldehyde fixed bovine pericardium: comparisons and evaluation of possible synergic effects. *Rev Bras Cir Cardiovasc* 21: 180-187.
53. Abolhoda A, Yu S, Oyarzun JR, Allen KR, McCormick JR, et al. (1996) No-react detoxification process: a superior anticalcification method for bioprostheses. *Ann Thorac Surg* 62: 1724-1730.
54. Carrel TP, Schoenhoff FS, Schmidli J, Stalder M, Eckstein FS, et al. (2008) Deleterious outcome of No-React-treated stentless valved conduits after aortic root replacement: why were warnings ignored? *J Thorac Cardiovasc Surg*. 136: 52-57.
55. Zhou J, Jiang H, Wang D, Hu S (2009) A novel anti-calcification strategy of bovine pericardium using sodium bisulfite modification. *J Heart Valve Dis* 18: 180-185.
56. Guldner NW, Jasmund I, Zimmermann H, Heinlein M, Girndt B, et al. (2009) Detoxification and endothelialization of glutaraldehyde-fixed bovine pericardium with titanium coating: a new technology for cardiovascular tissue engineering. *Circulation* 119: 1653-1660.
57. Fleisch H, Bisaz S (1962) Isolation from urine of pyrophosphate, a calcification inhibitor. *Am J Physiol* 203: 671-675.
58. Chang HW, Kim SH, Kim KH, Kim YJ (2011) Combined anti-calcification treatment of bovine pericardium with amino compounds and solvents. *Interact Cardiovasc Thorac Surg* 12: 903-907.
59. Ohri R, Hahn SK, Hoffman AS, Stayton PS, Giachelli CM (2004) Hyaluronic acid grafting mitigates calcification of glutaraldehyde-fixed bovine pericardium. *J Biomed Mater Res A* 70: 328-334.
60. Leirner AA, Tattini V Jr, Pitombo RN (2009) Prospects in lyophilization of bovine pericardium. *Artif Organs* 33: 221-229.
61. Fleisch HA, Russell RG, Bisaz S, Mühlbauer RC, Williams DA (1970) The inhibitory effect of phosphonates on the formation of calcium phosphate crystals *in vitro* and on aortic and kidney calcification *in vivo*. *Eur J Clin Invest* 1:12-18.
62. Kennedy JA, Hua X, Mishra K, Murphy GA, Rosenkranz AC, et al. (2009) Inhibition of calcifying nodule formation in cultured porcine aortic valve cells by nitric oxide donors. *Eur J Pharmacol* 602: 28-35.
63. Gordge MP, Xiao F (2010) S-nitrosothiols as selective antithrombotic agents - possible mechanisms. *Br J Pharmacol* 159: 1572-1580.
64. Sucu N, Tamer L, Aytacoglu B, Polat A, Dondas HA, et al. (2004) Inhibition of calcification with citric acid in pericardial bioprosthetic heart valve material: a preliminary report. *J Heart Valve Dis* 13: 697-700.
65. Kim KC, Kim SH, Kim YJ (2011) Detoxification of Glutaraldehyde Treated Porcine Pericardium Using L-arginine & NABH₄. *Korean J Thorac Cardiovasc Surg* 44: 99-107.
66. Braile MC, Carnevalli NC, Goissis G, Ramirez VA, Braile DM (2011) *In vitro* properties and performance of glutaraldehyde-crosslinked bovine pericardial bioprostheses treated with glutamic acid. *Artif Organs* 5: 497-501.
67. Weissenstein C, Human P, Bezuidenhout D, Zilla P (2000) Glutaraldehyde detoxification in addition to enhanced amine cross-linking dramatically reduces bioprosthetic tissue calcification in the rat model. *J Heart Valve Dis* 9: 230-240.
68. Connolly JM, Alferiev I, Kronsteiner A, Lu Z, Levy RJ (2004) Ethanol inhibition of porcine bioprosthetic heart valve cusp calcification is enhanced by reduction with sodium borohydride. *J Heart Valve Dis* 13: 487-493.
69. Maizato MJ, Hayashida SA, Taniguchi FP, Higa OZ, Pitombo RN, et al. (2011) *In vitro* and *in vivo* evaluation of lyophilized bioprosthetic valve. *Artif Organs* 35: 490-496.
70. Santibáñez-Salgado JA, Olmos-Zúñiga JR, Pérez-López M, Aboitiz-Rivera C, Gaxiola-Gaxiola M, et al. (2010) Lyophilized glutaraldehyde-preserved bovine pericardium for experimental atrial septal defect closure. *Eur Cell Mater* 19: 158-165.
71. Pathak CP, Adams AK, Simpson T, Phillips RE Jr, Moore MA (2004) Treatment of bioprosthetic heart valve tissue with long chain alcohol solution to lower calcification potential. *J Biomed Mater Res A* 69: 140-144.
72. Pettenazzo E, Valente M, Thiene G (2008) Octanediol treatment of glutaraldehyde fixed bovine pericardium: evidence of anticalcification efficacy in the subcutaneous rat model. *Eur J Cardiothorac Surg* 34: 418-422.
73. Sucu N, Karaca K, Yilmaz N, Cömelekoglu U, Aytacoglu BN, et al. (2006) Two stage EDTA anti-calcification method for bioprosthetic heart valve materials. *Med Sci Monit* 12: 33-38.
74. Musey PI, Ibim SM, Talukder NK (2002) Development of artificial blood vessels: seeding and proliferation characteristics of endothelial and smooth muscle cells on biodegradable membranes. *Ann N Y Acad Sci* 961: 279-283.
75. Ravi S, Chaikof EL (2010) Biomaterials for vascular tissue engineering. *Regen Med* 5: 107.
76. Fischer K, Kraner-Scheiber S, Petersen B, Rieblinger B, Buermann A, et al. (2016) Efficient production of multi-modified pigs for xenotransplantation by 'combineering', gene stacking and gene editing. *Sci Rep*. 6: 29081.
77. Conlan JV, Vongxay K, Jarman RG, Gibbons RV, Lunt RA, et al. (2012) Serologic study of pig-associated viral zoonoses in Laos. *Am J Trop Med Hyg* 6: 1077-1084.